arXiv:cond-mat/0509510v1 [cond-mat.mtrl-sci] 20 Sep 2005

Unusual polymerization in the Li_4C_{60} fulleride

M. Riccò,* T. Shiroka, M. Belli, D. Pontiroli, and M. Pagliari
Dipartimento di Fisica and Istituto Nazionale di Fisica della Materia, Università di Parma, Parco Area delle Scienze 7/a, 43100 Parma, Italy

G. Ruani and D. Palles†
Istituto ISMN-CNR, Via P. Gobetti 101, 40129 Bologna, Italy

S. Margadonna
School of Chemistry, University of Edinburgh, West Mains Road, EH9 3JJ Edinburgh, UK

M. Tomaselli
Laboratory of Physical Chemistry, ETH-Hönggerberg, Pauli Strasse 10, CH-8093, Zürich, Switzerland
(Dated: February 2, 2008)

Li_4C_{60}, one of the best representatives of lithium intercalated fullerides, features a novel type of 2D polymerization. Extensive investigations, including laboratory x-ray and synchrotron radiation diffraction, ^{13}C NMR, MAS and Raman spectroscopy, show a monoclinic $I2/m$ structure, characterized by chains of [2+2]-cycloaddicted fullerenes, sideways connected by single C–C bonds. This leads to the formation of polymeric layers, whose insulating nature, deduced from the NMR and Raman spectra, denotes the complete localization of the electrons involved in the covalent bonds.

PACS numbers: 81.05.Tp, 82.35.Lr, 61.48.+c, 82.56.Ub, 78.30.Na

I. INTRODUCTION

Extensive investigations of fullerene C_{60}, both in its pristine form as well as in its intercalated variants, have definitively confirmed the strong tendency toward polymerization of this molecule. Indeed, the original cubic van der Waals bonded fcc structure of solid C_{60} can easily be transformed into 1-, 2-, and even 3-dimensionally connected polymers either by photo-excitation,[1] or by high-temperature and high-pressure[2,3] treatments.

The polymeric forms of C_{60} have attracted considerable attention mainly because of the variety of crystal structures and their interesting magnetic, optical and mechanical properties. Notably, ferromagnetism with Curie temperature above 500 K has recently been reported in the rhombohedral phase of the 2D-polymer.[4,5] On the other hand, the intercalation of solid C_{60} with electron donors like alkali metals (A), has resulted in a wealth of fulleride salts with stoichiometries A_xC_{60}, among which superconducting A_3C_{60} have received extended attention. The intercalation of alkali metals itself can, in few cases, induce the formation of 1D or 2D arrangements of polymerized C_{60}. In particular, A_1C_{60} (A = K, Rb, Cs) can display chains of fullerenes linked by "double" C–C bonds ([2+2]-cycloaddition),[6,7,8] while 1D or 2D arrangements of singly bonded C_{60} have been observed in Na_2RbC_{60}[9,10] or Na_4C_{60}.[11,12]

If compared with other better known alkali-doped fullerides, lithium intercalated compounds Li_xC_{60} display quite different properties, which can be mainly ascribed to the small Li-ion dimensions and to the partial charge transfer from the Li-atoms. The most relevant differences, addressed only in recent years,[13,14,15,16,17] concern the large doping range ($x = 1 \div 30$), the lack of superconductivity and the formation of polymerized C_{60} structures.[15]

Lithium-doped fullerenes themselves behave differently depending on the amount of intercalated lithium. At high doping levels (typically for $x > 7$) both diffraction[16] and multiple quantum NMR[17] clearly show the formation of lithium clusters located in the largest interstices of the C_{60} fcc lattice, with all the members of this subclass having similar properties. However, as the lithium concentration decreases below $x = 7$, the volume occupied by the intercalants decreases, while the efficiency of charge transfer is expected to increase. Both these factors lead to a reduction of the inter-fullerene distance, and if two facing carbon atoms get close enough, covalent bonds are formed giving rise to fullerene polymerization.

In this paper we extensively investigate Li_4C_{60}, which is the most representative member of this family by diffraction (laboratory and synchrotron) techniques, as well as ^{13}C static NMR, magic angle spinning (MAS) NMR and Raman spectroscopy. The polymerization seems to occur as a consequence of the "positive" chemical pressure exerted by Coulomb interaction, leading to a novel 2D polymerization pattern, characterized by the coexistence of single and "double" C–C bonds propagating along two orthogonal directions of the plane. Detailed NMR lineshape analysis and Raman measurements, besides confirming the structure, show beyond doubt the presence of an insulating phase, arising from the electron localization in the covalent bonds.

II. EXPERIMENTAL METHODS

Li_xC_{60} samples ($1 \leq x \leq 6$) were prepared either by thermal decomposition of Li azide or by direct doping with lithium metal. In the former case a mixture of stoichiometric amounts of lithium azide and C_{60} powder was heated up to ~ 510 K under dynamical vacuum. In the second case a pellet of metallic lithium and C_{60} powder was heated up to ~ 540 K and, after several regrinding and pelleting cycles, a homogeneously doped sample is eventually obtained. Preliminary x-ray characterization showed that both methods yielded good quality samples having the same structure.

Laboratory x-ray diffraction was performed with a Bruker D8 diffractometer equipped with a double Göbel mirror monochromator and a GADDS position sensitive detector (Cu Kα radiation), whereas synchrotron diffraction experiments were performed on the ID31 beamline at ESRF (Grenoble). In both cases the samples were sealed in 0.5 mm quartz capillaries.

An AMX 400 Bruker workstation, equipped for solid state NMR experiments, was used for the static ^{13}C NMR measurements. The spectra were collected employing a standard Hahn echo pulse sequence (90°–τ–180°) with $\tau = 100$ μs and a recycle delay of 200 s. Magic angle spinning (MAS) ^{13}C NMR measurements were performed with a home-built instrument. In this case the Hahn echo spectra were taken using a τ delay equal to twice the rotor period at a spinning rate of 5 kHz and 8 kHz respectively, with a recycle delay of 10 s.

Micro-Raman spectra at room temperature were recorded in a back-scattering geometry using a Renishaw 1000 and a T64000 Jobin-Yvon spectrometers, both equipped with charge coupled device (CCD) cameras and microscope lenses with ×100 and ×50 magnification. In both cases the resolution was ~ 1.0 cm^{-1} and the accuracy better than 0.5 cm^{-1}. The excitation was provided by the 488.0 nm and 514.5 nm lines of an Ar^+ laser or the 632 nm line of a He-Ne laser. The laser beam was focused on the sample in a spot of ~ 2 μm in diameter (×100 lens), while the power level was kept below 50 μW to avoid photo-degradation effects. In the adopted scattering geometry the polarization of the incident and scattered light were parallel to each other. Accumulation times of several hours were needed to compensate for the very low levels of scattered light due to the low laser power.

III. RESULTS AND DISCUSSION

A. Structural investigation

Laboratory x-ray diffraction measurements were performed on the whole Li_xC_{60} series with $1 \leq x \leq 6$. The diffraction patterns show that for $x \leq 2$ and $x = 6$ the samples consists of at least two phases, one of which is pristine C_{60} which did not take part into the reaction (see Fig. 1). On the other hand, for intermediate stoichiometries $3 \leq x \leq 5$, the compounds appear homogeneous and with the same structure. In fact, unlike other alkali doped fullerides (as e.g. K_xC_{60}), where the presence of line phases is observed, the structural properties of Li_xC_{60} seem to depend weakly on stoichiometry. Since Li_4C_{60} is expected to be the most representative member of this family, detailed investigations were performed on samples having $x = 4$.

Room temperature synchrotron radiation diffraction of Li_4C_{60}[18] (see Fig. 2) shows that its structure is body

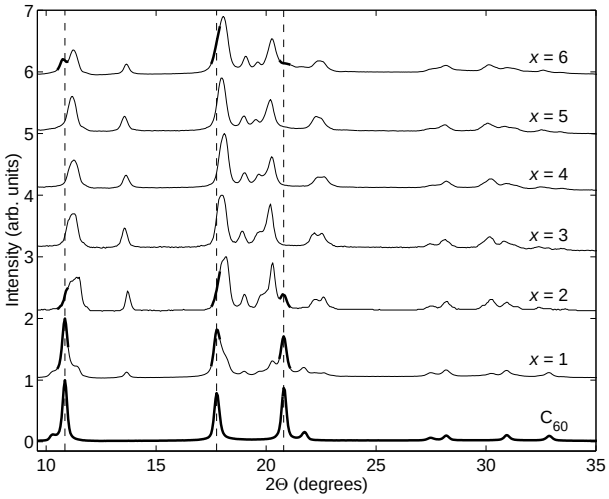

FIG. 1: Room temperature Li_xC_{60} powder diffraction patterns taken with Cu Kα laboratory x-rays for $1 \leq x \leq 6$. For $x = 1$, 2, 6 there is a clear phase co-existence (bold lines), whereas for $3 \leq x \leq 5$ the samples are homogeneous. For comparison the pristine C_{60} diffraction profile and its main peak positions (dashed lines) are also shown.

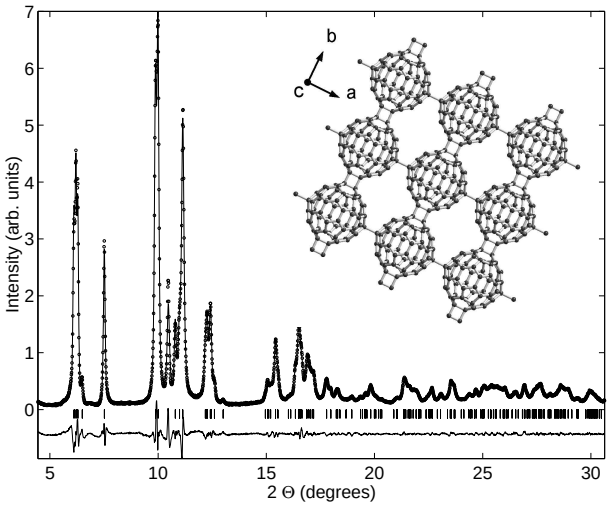

FIG. 2: Measured (o) and calculated (solid line) diffraction pattern of Li_4C_{60} at 300 K. The lower solid line shows the difference profile and the ticks mark the reflection positions. Inset: the polymeric structure of Li_4C_{60}.

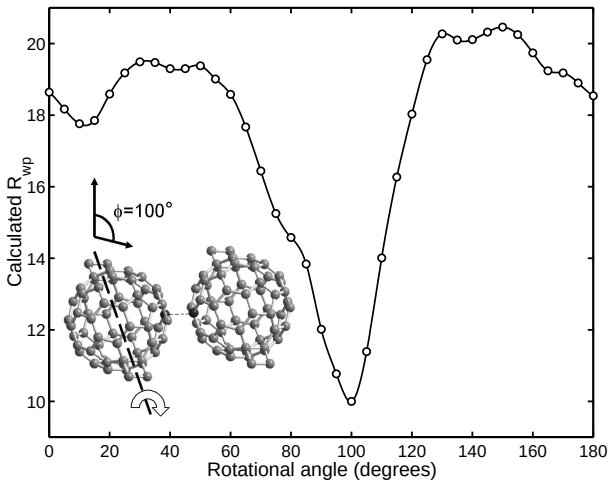

FIG. 3: Fit residuals $R_{\rm wp}$ as fullerene chains rotate along the b axis. The minimum at $\sim 100^\circ$ corresponds to neighboring C atoms facing each other and giving rise to single bond polymerization (see inset).

centered monoclinic (space group *I2/m*) with the following lattice parameters and angle: $a = 9.3267(3)$ Å, $b = 9.0499(3)$ Å, $c = 15.03289(1)$ Å, $\beta = 90.949(3)^\circ$. The analysis with the Le Bail pattern decomposition technique provides $R_{\rm wp} = 4.24\%$ and $R_{\rm exp} = 1.53\%$. If center-to-center distances between the nearest C_{60} units are considered, it turns out that along the b direction the contact distance (~ 9.05 Å) is similar to that encountered in other polymerized A_1C_{60}, thus suggesting the presence of two bridging C–C bonds.

The Rietveld refinement, starting from a structure derived from RbC_{60}, characterized by linear polymeric inter-fullerene chains directed along the b axis,[19,20] indicates that the fit quality strongly depends on the fullerene arrangement with respect to chain rotations along the [010] crystallographic directions. In particular, the fit residual $R_{\rm wp}$ shows a deep minimum when the angle ϕ with the initial direction becomes $\sim 100^\circ$ (see inset in Fig. 3).

At this angle, the arrangement of C_{60} molecules is such that *pairs of carbon atoms* on fullerenes belonging to neighboring chains are found very close (~ 2 Å) to each other. This strongly suggests that for a suitable orientation of the buckyballs not only the usual polymerization via the [2 + 2]-cycloaddition reaction along b direction can take place, but also a connection through single C–C bonds along the a axis is also possible. The minimum $R_{\rm wp}$ (5.12%) in the final Rietveld analysis was obtained by refining the positions of the whole C_{60} atoms by the use of soft constrains. It corresponds to a single inter-fullerene bond length of 1.75(2) Å directed along the a axis and to a bond inclination of $\sim 2^\circ$ with respect to the ab plane.

In an effort to localize the lithium atoms positions, the experimental diffraction pattern was investigated using Fourier analysis. The maxima of the electronic density map show that two lithium ions are located near the pseudo-tetrahedral site at (0.416, 0, 0.748), whereas the other two Li^+ ions per fullerene are found in the (0.023, 0, 0.380) and (−0.023, 0, 0.620) positions respectively, symmetrically displaced along the c direction with respect to the center of the pseudo-octahedral site. In both cases the reported values refer to the average lithium positions, as confirmed by the high isotropic temperature factor ($B_{\rm iso} \sim 11$) and the smooth maxima in the Fourier map.

B. NMR spectroscopy

The uniqueness of the proposed Li_4C_{60} structure requires a rigorous and systematic proof also by other independent investigations. Static and MAS (Magic Angle Spinning) ^{13}C NMR measurements provided such a kind of independent evidence which fully confirmed the previous results.

The room temperature static spectrum of Li_4C_{60}, referenced to tetramethyl silane (TMS), is shown in Fig. 4 along with a reference spectrum of pristine C_{60}. The lineshape consists of a broad powder pattern, arising from the chemical shielding tensor, and a relatively narrow peak at lower frequencies which, at the intrinsic resolution of the static spectrum, does not exhibit any peculiar feature. The broad pattern is located in a frequency domain commonly attributed to sp^2 hybridized carbon atoms, whereas the narrow peak falls in the region of sp^3 carbons.[21]

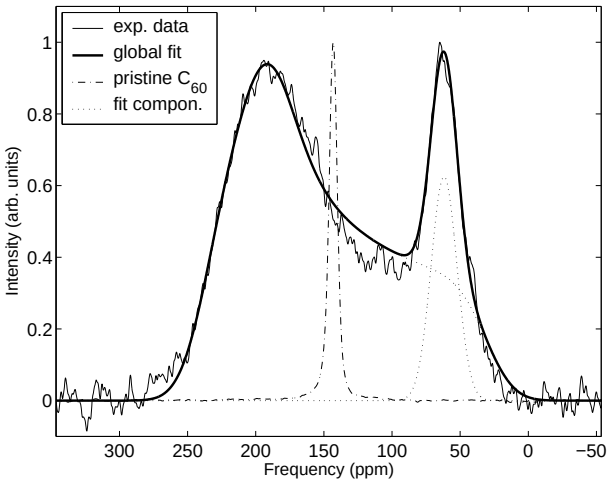

FIG. 4: ^{13}C static NMR spectrum of Li_4C_{60} at room temperature along with the global fit and its two components (a Gaussian function and a chemical shielding powder pattern). The narrow peak of pristine C_{60} at 143 ppm is also shown.

The lack of motional narrowing, typically observed in the room temperature C_{60} rotator phase, indicates that in the as-prepared Li_4C_{60} the fullerene molecules are ro-

tationally frozen. At the same time, the presence of an sp^3 peak at ~ 60 ppm confirms the formation of covalent bonds among C_{60} units. A rough estimate of the number of carbon atoms involved in the bonds can be obtained by analyzing the integrated intensity of the different components of the spectrum. To this aim the spectra were fitted with a simple model, comprising a single chemical shift tensor pattern and an additional Gaussian peak. The ratio of the integrated intensities of the two fit components is respectively $1:8(1)$, a result which is in good agreement with the expected $1:9$ ratio (6 carbon atoms involved in the bonds and 54 sp^2-hybridized carbons per C_{60} molecule).

A more detailed analysis of the sp^2 component was not possible, since the contributions arising from the 14 inequivalent carbon atoms[18] are not resolved in the static spectrum. Nevertheless, the tensor components can be considered as a rough average of the different contributions, enabling us to make useful comparisons with the carbon NMR spectra of other alkali-doped fullerides. In particular, it is possible to obtain important clues about the nature of the global shift tensor $\boldsymbol{\delta}$, which represents the sum of the chemical shielding tensor $\boldsymbol{\sigma_{CS}}$, arising from nucleus interaction with the orbital electrons, and the Knight shift tensor $\boldsymbol{K}$, originating from nucleus interaction with the delocalized conduction electrons. Thus, information about the electronic transport properties of Li_4C_{60} can be directly extracted from the ^{13}C NMR measurements.

For an easier interpretation, the fitted $\boldsymbol{\delta}$-tensor components $[\delta_{xx}\ \delta_{yy}\ \delta_{zz}] = [237\ 191\ 31]$ can be conveniently separated into an isotropic part $\delta_{\rm iso} = (\delta_{xx}+\delta_{yy}+\delta_{zz})/3$ and an anisotropic traceless tensor $\boldsymbol{\delta_{aniso}} = \boldsymbol{\delta} - \boldsymbol{\delta_{iso}}$ (the convention adopted is $|\delta_{zz}-\delta_{\rm iso}| \geq |\delta_{yy}-\delta_{\rm iso}| \geq |\delta_{xx}-\delta_{\rm iso}|$). As far as the isotropic part is concerned, the value we find in the Li_4C_{60} case, $\delta_{\rm iso} = +153$ ppm, is quite close to the isotropic chemical shift value $\sigma_{\rm iso} = +143$ ppm of pristine C_{60},[22] which, being the pure C_{60} an insulator, coincides with its $\delta_{\rm iso}$. In alkali-doped fullerenes, where the molecule is found as a C_{60}^{n-} counter-ion, $\sigma_{\rm iso}$ is expected to increase slightly as a function of doping reaching ~ 150 ppm for $n = 3$,[23] whereas $K_{\rm iso}$ for conducting fullerides is ~ 40 ppm.[23,24] The closeness of the measured $\delta_{\rm iso}$ to that of pure C_{60} implies the lack of an *isotropic* Knight shift in the static spectrum of Li_4C_{60}, a conclusion that is fully consistent with the MAS results (*vide infra*).

On the other hand, a contribution arising from the *anisotropic* part of the Knight shift is still possible. The traceless component of the fitted tensor is $[84\ 38\ -122]$, implying an anisotropy parameter $\Omega = \delta_{zz} - \delta_{iso} = -122$ ppm. The traceless tensor represents the sum of the traceless chemical shielding tensor $\boldsymbol{\sigma_{aniso}}$ and the traceless Knight shift tensor $\boldsymbol{K_{aniso}}$, generally opposite in sign (we assume that the principal axes coincide for the two tensors). Typical values for chemical shielding anisotropy defined as $\Omega_{\rm CS} = \sigma_{zz} - \sigma_{iso}$ in alkali-metal doped fullerides fall around -110 ppm (and do not differ significantly from the chemical shielding anisotropy in pristine C_{60}),[22] while in metallic fullerides $\Omega_{\rm K}$ goes from +160 up to +200 ppm.[23] From the comparison of our measurement with the values taken from the literature we conclude that also the Knight shift traceless tensor is negligible for Li_4C_{60}.

The analysis of both the isotropic and anisotropic components of the sp^2 part of the spectrum represents therefore a convincing proof of the insulating nature of the Li_4C_{60} polymer at room temperature.

Finally, we note that the complete absence of a sharp peak near +143 ppm, even with long recycle delays, implies the lack of unreacted C_{60} in the sample, in agreement with the single phase evidenced by diffraction data.

Further insights come from the ^{13}C MAS spectrum, where the anisotropy of the different interactions is averaged out, just like in NMR in solutions, and only the isotropic shifts are measured.

A MAS measurement on Li_4C_{60} using an 8 kHz spinning rate is reported in Fig. 5. The spectrum consists of a rather broad sp^2 multiplet, spanning the region from ~ 85 MHz up to ~ 210 MHz, and two well resolved peaks in the sp^3 hybridized carbon region, at +57 ppm and +62 ppm respectively. By comparing the present spectrum with that obtained at a lower spinning rate (5 kHz, not shown here) allowed us to identify the satellite lines of the sp^2 multiplet with the region which includes the small peaks from ~ 210 ppm to ~ 300 ppm and the broad basis below the two sp^3 peaks. On the other hand, the satellite lines originating from the sp^3 peaks had a negligible amplitude and were not considered.

The relatively close spacing of the sp^2 multiplet components, along with the low spinning rate imposed by geometrical constraints, prevented us from unambiguously assigning the sp^2 peaks to each of the 14 structurally inequivalent sp^2 carbon atoms; nevertheless some interesting conclusions can be drawn.

The whole spectrum can be interpreted as follows: the polymerization induces a distortion of the buckyballs, thus different sp^2 carbon atoms are characterized by slightly different isotropic chemical shifts, clearly visible in the MAS spectrum. On the other hand, the two different peaks in the sp^3 carbon region are reminiscent of the two different kinds of covalent bonds, which we can easily identify with the single bond along the a direction and the four-membered carbon ring, analogous to a "double" bond, along the b direction. Indeed, the integrated intensity ratio of these peaks is approximately $1:2$, in agreement with the number of carbon atoms involved in the bonds. Moreover, the lower frequency of the smaller sp^3-like peak reflects its single bond nature, since in this case the more spherical hybridization acts as a better shield to the external field.

As a conclusion, both static and MAS ^{13}C NMR data fully support not only the presence of polymerization in Li_4C_{60}, but also the complex and unusual bonding motif among the buckyballs. In addition to carbon NMR we performed also ^{7}Li static NMR measurements.[25] The

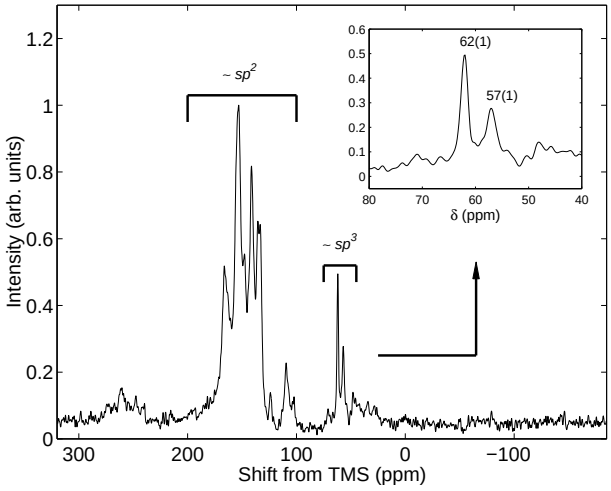

FIG. 5: ^{13}C MAS (8 kHz) spectrum at 300 K showing the different intensities for sp^2 and sp^3 carbon atoms. Insert: the two peaks in the sp^3 region arise from two different types of C_{60} polymerization.

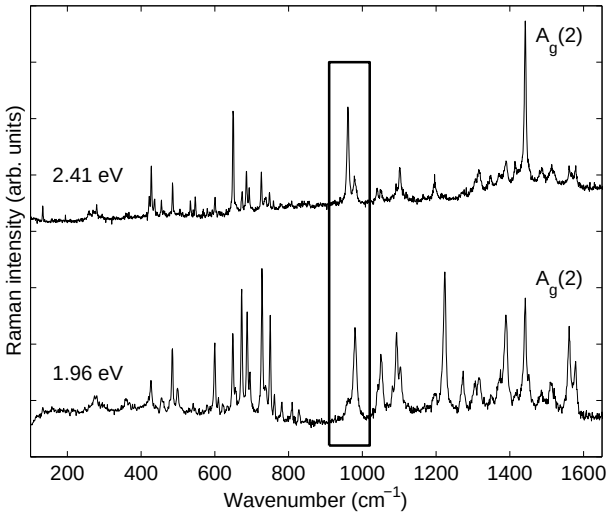

FIG. 6: Room temperature micro-Raman spectra of Li_4C_{60} in a parallel polarization scattering geometry and for two laser excitation energies: 2.41 eV and 1.96 eV. The two peaks arising from carbon polymerization are shown in the boxed area.

room temperature spectrum (not shown here) consisted of a single peak with an isotropic shift of approximately -1 ppm with respect to a saturated LiCl:aq reference solution. The nutation angle analysis led to the conclusion that it is a motionally narrowed peak, confirming once more the rather high mobility of Li atoms at room temperature and the fact that x-ray diffraction can only identify their average positions.

C. Raman spectroscopy

The presence in fullerenes of ten Raman active modes (the A_g and H_g modes) makes Raman spectroscopy one of the preferred tools to study their dynamical and structural properties.[26,27] In a crystal, however, the selection rules derived from the high icosahedral symmetry of C_{60} are somewhat relaxed, and several of the previously forbidden modes acquire Raman activity. It is on some of these 'new' lines, which have become fingerprints of solid state phenomena like polymerization and dimerization, where we focus our attention.

In the Raman spectra of undoped polymeric C_{60}, the double peak in the region 940–980 cm^{-1} has been assigned to the stretching vibrations of the four carbon atoms participating in the bridging [2+2] bonds between neighboring C_{60} cages and is considered as a signature of polymeric C_{60}.[28] Indeed, it is present both in the tetragonal[29] (946 and 974 cm^{-1}, $\Delta\omega = 28$ cm^{-1}) as well as rhombohedral[4] (959 and 978 cm^{-1}, $\Delta\omega = 19$ cm^{-1}) phases of C_{60}. Nevertheless, the surprising presence of similar peaks (966 and 980 cm^{-1}, $\Delta\omega = 14$ cm^{-1}) also in the polymerized *single* C–C bond Na_4C_{60},[29] with a monoclinic two-dimensionally linked structure, has put serious doubts on the exclusive assignment of these peaks to the ring stretch vibrations. Currently they tend to be associated with the more generic presence of sp^3-type intermolecular bonds.

The Raman spectra of Li_4C_{60}, synthesized by direct Li metal doping, are shown in Fig. 6. As expected, the presence of polymerization sp^3 bonds gives rise to both the characteristic peaks (961 cm^{-1} and 979 cm^{-1}, $\Delta\omega = 18$ cm^{-1}), with positions and splitting very similar to those of rhombohedral C_{60}. Differently from what is found in the Na_4C_{60} case, though, where both peaks have similar amplitudes and their relative heights do not change with laser excitation energy, in our case the analogous peak heights depend strongly on laser wavelength (see boxed area in Fig. 6). This can be easily rationalized if the complete equivalence of carbon bonds in the first case, and their mixed nature in the latter, is taken into account.

A further confirmation about the lowered symmetry of the mixed polymeric structure, due to the presence of single bonds in one direction and "double" C–C bonds in the orthogonal direction, as well as to a possible crystal field distortion due to the intercalated Li atoms, is found in the increased complexity of the Raman spectrum. Indeed, in the low symmetry crystal structure of Li_4C_{60} at least 41 discernible bands can be recognized, to be compared with e.g. the higher symmetry tetragonal polymeric C_{60}, with only ~ 23 discernible bands (excluding very weak ones).[29] Moreover, also three low energy modes (which are silent in the highly symmetric crystalline C_{60}) and attributed to intramolecular stretching are observed as well at 133, 158 and 195 cm^{-1}.

The Raman spectra of Li_4C_{60} are generally characterized by narrow peaks, indicating both an ordered structure and a negligible electron phonon interaction, as in the case of non metallic systems.[30] In particular, the band

assigned to the $A_g(2)$ parent mode, located at 1442 cm^{-1} (see Fig. 6), is very narrow (< 6 cm^{-1}), confirming the presence of a single phase fulleride.

Since many of the Raman peaks of Li_4C_{60} appear either in the tetragonal two-dimensional polymeric C_{60} (characterized by "double" C–C bonds) or in the monoclinic two-dimensional polymeric network of Na_4C_{60} (characterized by single C–C bonds), we can infer the mixed nature of our sample, in agreement with the results from x-ray diffraction. We point out, however, that although the present Raman spectrum is practically identical to that of Li_4C_{60} reported in Ref. 31, the latter was characterized as a two-dimensional "*double*" bond polymer.

The energy dependence of the $A_g(2)$ mode of C_{60} (located at 1469 cm^{-1} for the pristine material) has been correlated approximately linearly with the amount of charge transferred to the C_{60} cage for the most studied alkali fullerides, A_xC_{60}, A = K, Cs, Rb, where the charge transfer has been verified independently using other experimental techniques. In this case an $A_g(2)$ mode softening by 6–7 cm^{-1} per electron transfer has been measured by Raman scattering.[32]

For polymeric C_{60}, on the other hand, the issue of charge transfer is complicated by the presence of covalent bonds between C_{60} units, which also causes a downshift of the $A_g(2)$ mode energy. According to the hypothesis reported in Ref. 29, the $A_g(2)$ mode energy downshift attributable to cage polymerization is ~ 2.5 cm^{-1} per single and ~ 5.5 cm^{-1} per "double" C–C bond. Under this assumption, the charge transferred to C_{60} in the Li_4C_{60} case should be $[1469-(2\times5.5+2\times2.5)-1442]/6 \approx 2e^-$, presumably arising from only a partial charge transfer. It remains therefore unclear whether the values of the $A_g(2)$ mode energy in Na_4C_{60} and Li_4C_{60} can indeed be explained by this 'rule' or if there exists in the polymeric systems some other mechanism that supersedes this simple additive rule and makes the identical $A_g(2)$ mode energies a direct consequence of a similar charge transfer in both cases.

It is known that for Li_xCsC_{60}[33] (and in part also for Na_xC_{60}[34]) only an incomplete charge transfer from the alkali to the C_{60} molecule takes place, in contrast to what is observed in other alkali metal doped fullerides.

In the case of Li_4C_{60} the large mobility of the Li atoms at room temperature, suggested by NMR measurements, is not compatible with the existence of hybrid electronic states between Li and C_{60}. Notably, Raman measurements performed in the high temperature monomeric phase of Li_4C_{60}, indicate a C_{60}^{-4} charge state.[35]

IV. CONCLUSIONS

In summary, the combination of powder diffraction analysis, NMR and Raman spectroscopies allowed us to precisely identify the structure as well as to probe the electronic properties of Li_4C_{60}, the best representative of low-doped lithium fullerides. A novel 2D polymeric arrangement with a mixed interfullerene bonding motif was found at room temperature. The formation of [2+2]-cycloaddicted fullerene chains sideways connected with single C–C bonds, suggested by the diffraction, is fully confirmed by NMR and Raman spectroscopy. The former shows two distinct sp^3 lines in the ^{13}C MAS spectrum whose intensity ratio agrees with the number of carbon atoms involved in the bonds, while the latter shows the presence of a doublet in the 940–980 cm^{-1} region, a well known fingerprint of fullerene polymers. Both ^{13}C and ^7Li NMR show the absence of Knight shift as well as any paramagnetic shift, clearly indicating that this polymer is a diamagnetic insulator. A measurement of the amount of charge transferred to C_{60} from the Raman $A_g(2)$ mode shift (a widely used method in alkali fullerides) cannot be reliably extended to fullerene polymers, where molecules are deformed by the presence of intermolecular bonds. Empirical rules[29] suggest in Li_4C_{60} only a partial transfer of two electrons, although diffraction Fourier analysis locates Li ions too far from the fullerene molecules to allow the hybridization of the $2s$ electron (as it was observed also in Li_xCsC_{60}[33]). This puts some doubts on the general application of these rules to different C_{60} polymer structures.

Acknowledgments

We thank Dr. C. Vignali of the Centro Interfacoltà Misure of Parma University for his valuable help with the static NMR experiments and acknowledge the financial support by the national FIRB project "New Materials and Mechanisms of Superconductivity in Fullerenes".

D.P. acknowledges the financial support by the European Commission through the T.M.R. network no. ERBFMRX-CT97-0155 "FULPROP" and the Greek State Scholarships Foundation (I.K.Y.).

* Electronic address: Mauro.Ricco@fis.unipr.it; URL: `http://www.fis.unipr.it/~ricco/`

† Permanent address: Department of Physics, School of Applied Sciences, National Technical University of Athens, Heroon Polytechneiou 9 st., 15780 Zografos, Greece.

[1] M. Núñez-Regueiro, L. Marques, J-L. Hodeau, O. Béthoux, and M. Perroux, Phys. Rev. Lett. **74**, 278 (1995).

[2] L. Marques, M. Mezouar, J.-L. Hodeau, M. Núñez-Regueiro, N.R. Serebryanaya, V.A. Ivdenko, V.D. Blank, and G.A. Dubitsky, Science, **283**, 1720 (1999).

[3] Y. Iwasa, T. Arima, R.M. Fleming, T. Siegrist, O. Zhou, R.C. Haddon, L.J. Rothberg, K.B. Lyons, H.L. Carter

Jr., A.F. Hebard, R. Tycko, G. Dabbagh, J.J. Krajewski, G.A. Thomas, and T. Yagi, Science **264**, 1570 (1994).
[4] T.L. Makarova, B. Sundqvist, P. Esquinazi, R. Höhne, Y. Kopelevich, P. Scharff, V. A. Davydov, L. S. Kashevarova, and A. V. Rakhmanina, Nature **413**, 716 (2001).
[5] R.A. Wood, M.H. Lewis, M.R. Lees, S.M. Bennington, M.G. Cain, and N. Kitamura, J. Phys.: Condens. Matter, **14**, L385 (2002).
[6] J. Winter and H. Kuzmany, Carbon, **36**, 599 (1998).
[7] O. Chauvet, G. Oszlányi, L. Forró, P. W. Stephens, M. Tegze, G. Faigel, and A. Jànossy, Phys. Rev. Lett. **72**, 2721 (1994).
[8] S. Pekker and G. Oszlányi, Synth. Metals **103**, 2411 (1999).
[9] G.M. Bendele, P.W. Stephens, K. Prassides, K Vavekis, K. Kordatos, and K. Tanigaki, Phys. Rev. Lett., **80**, 736 (1998).
[10] D. Arčon, K. Prassides, S. Margadonna, A.-L. Maniero, L. C. Brunel, and K. Tanigaki, Phys. Rev. B **60**, 3856 (1999).
[11] G. Oszlányi, G. Baumgartner, G. Faigel, and L. Forró, Phys. Rev. Lett. **78**, 4438 (1997).
[12] A. Rezzouk, F. Rachdi, Y. Errammach, and J.L. Sauvajol, Physica E, **15**, 107 (2002).
[13] M. Yasukawa and S. Yamanaka, Chem. Phys. Lett. **341**, 467 (2001).
[14] Y. Maniwa, H. Ikejiri, H. Tou, M. Yasukawa, and S. Yamanaka, Synth. Metals **121**, 1105 (2001).
[15] M. Tomaselli, B. H. Meier, M. Riccò, T. Shiroka, and A. Sartori, Phys. Rev. B **63**, 113405 (2001).
[16] L. Cristofolini, M. Riccò, and R. De Renzi, Phys. Rev. B **59**, 8343 (1999).
[17] M. Tomaselli, B. H. Meier, M. Riccò, T. Shiroka, and A. Sartori, J. Chem. Phys. **115**, 472 (2001).
[18] S. Margadonna, D. Pontiroli, M. Belli, T. Shiroka, M. Riccò, and M. Brunelli, J. Am. Chem. Soc. **126**, 15032 (2004).
[19] H.M. Guerrero, R.L. Cappelletti, D.A. Neumann, and T. Yildrim, Chem. Phys. Lett. **297**, 265 (1998).
[20] A. Huq, P.W. Stephens, G.M. Bendele, and R.M. Ibberson, Chem. Phys. Lett. **347**, 13 (2001).
[21] K.-F. Thier, M. Mehring, and F. Rachdi, Phys. Rev. B **55**, 124 (1997).
[22] R. Tycko, G. Dabbagh, R.M. Fleming, R.C. Haddon, A.V. Makhija, and S.M. Zahurak, Phys. Rev. Lett. **67**, 1886 (1991).
[23] N. Sato, H. Tou, Y. Maniwa, K. Kikuchi, S. Suzuki, Y. Achiba, M. Kosaka, and K. Tanigaki, Phys. Rev. B **58**, 12433 (1998).
[24] C.H. Pennington and V.A. Stenger, Rev. Mod. Phys., **68**, 855 (1996).
[25] M. Riccò, T. Shiroka, O. Ligabue, M. Belli, D. Pontiroli, G. Ruani, D. Palles and S. Margadonna, in *Proceedings of the International Symposium on Fullerenes, Nanotubes and Carbon Nanoclusters*, edited by P. V. Kamat, D. M. Guldi, F. D'Souza, (Electrochem. Soc., New York, USA) **615**, 463 (2003).
[26] H. Kuzmany, R. Pfeiffer, M. Hulman, and C. Kramberger, Phil. Trans. A: Math. Phys. Eng. Sci., **362**, 2375 (2004).
[27] H. Kuzmany, B. Burger, and J. Kürti, in *Optical and Electronic Properties of Fullerenes and Fullerene-Based Materials*, edited by J. Shinar, Z.V. Vardeny, Z.H. Kafafi, (Marcel Dekker, New York, 1999).
[28] G.B. Adams and J.B. Page, Phys. Stat. Solid **226**, 95 (2001).
[29] T. Wågberg and B. Sundqvist, Phys. Rev. B **65**, 155421 (2002).
[30] B. Friedl, C. Thomsen, H.U. Habermeier, and M. Cardona, Solid State Commun. **81**, 989 (1992).
[31] T. Wågberg, P. Stenmark, and B. Sundqvist, J. Phys. Chem. Solids **65**, 317 (2004).
[32] J.S. Duclos, R.C. Haddon, S. Glarum, A.F. Heberd, and K.B. Lyons, Science **254**, 1625 (1991).
[33] M. Kosaka, K. Tanigaki, K. Prassides, S. Margadonna, A. Lappas, C.M. Brown, and A.N. Fitch, Phys. Rev. B **59**, R6628 (1999).
[34] W. Andreoni, P. Giannozzi, J.F. Armbruster, M. Knupfer, and J. Fink, Europhys. Lett. **34**, 699 (1996).
[35] M. Riccò, M. Belli, D. Pontiroli, T. Shiroka, G. Ruani, D. Arčon, and S. Margadonna, manuscript in preparation.